

Removal of cationic dye methylene blue (MB) from aqueous solution by Coffee and Peanut husk Modified with Magnetite Iron Oxide Nanoparticles

Naereh Besharati¹, Nina Alizadeh^{1*}, Shahab Shariati²

¹ Department of Chemistry, University of Guilan, Namjoo Street, P.B.41335–1914, Rasht, Iran.

² Department of Chemistry, Islamic Azad University Rasht Branch, Rasht, Iran.

* Corresponding author: Tel/Fax:+9833333262, e-mail: n-alizadeh@guilan.ac.ir

Received December 13th, 2017; Accepted August 29th, 2018.

DOI: <http://dx.doi.org/10.29356/jmcs.v62i3.433>

Abstract. This study was focused on the adsorption of methylene blue (MB) as a cationic dye on magnetite nanoparticles loaded with coffee (MNLC) and magnetite nanoparticles loaded with peanut husk (MNLPH) as naturally cheap sources of adsorbent. Coffee and Peanut husk were magnetically modified by contact with water-based magnetic fluid. These new type of magnetically natural materials can be easily separated by means of magnetic separators. They were characterized with Fourier transform infrared spectroscopy (FT-IR), powder X-ray diffraction (XRD) and scanning electron microscopy (SEM) instruments. Different parameters affecting MB removal efficiency such as contact time, pH of solution and amount of adsorbents were studied and optimized. Dye adsorption process was studied from both kinetic and equilibrium point. The studies of MB sorption kinetic showed rapid dynamic sorption with second-order kinetic model, suggesting chemisorption mechanism with $R^2 = 0.9988$, $q_{eq}=10.28 \text{ mg g}^{-1}$ and $R^2=0.9967$, $q_{eq}=128.20 \text{ mg g}^{-1}$, respectively. Equilibrium data were fitted well to the Langmuir isotherm more than Freundlich and Temkin isotherm. The modified adsorbents showed MB removal with 88.49 and 74.62 mg g^{-1} sorption capacity for MNLC and MNLPH, respectively. This study showed a simple, efficient and reliable method for removal of MB from aqueous solutions with MNLC and MNLPH as efficient adsorbents.

Keywords: Methylene blue; Coffee; Peanut husk; Magnetic nanoparticles.

Resumen. Este estudio se centró en la adsorción de azul de metileno (MB) como un colorante catiónico en nanopartículas de magnetita cargadas con café (MNLC) y nanopartículas de magnetita cargadas con cáscara de cacahuete (MNLPH) como fuentes de adsorbente naturalmente económicas. El café y la cáscara de maní se modificaron magnéticamente por contacto con un fluido magnético a base de agua. Este nuevo tipo de materiales magnéticamente naturales se puede separar fácilmente mediante separadores magnéticos. Se caracterizaron con espectroscopia infrarroja de transformada de Fourier (FT-IR), difracción de rayos X en polvo (DRX) y microscopía electrónica de barrido (SEM). Se estudiaron y optimizaron diferentes parámetros que afectan la eficiencia de eliminación de MB, como el tiempo de contacto, el pH de la solución y la cantidad de adsorbentes. Se estudió el proceso de adsorción de tinte desde el punto de equilibrio y cinético. Los estudios de cinética de absorción de MB mostraron una absorción dinámica rápida con un modelo cinético de segundo orden, lo que sugiere un mecanismo de quimiosorción con $R^2= 0.9988$, $q_{eq}= 10.28 \text{ mg g}^{-1}$ y $R^2= 0.9967$, $q_{eq}= 128.20 \text{ mg g}^{-1}$, respectivamente. Los datos de equilibrio se ajustaron bien a la isoterma de Langmuir más que a la isoterma de Freundlich y Temkin. Los adsorbentes modificados mostraron eliminación de MB con 88.49 y 74.62 mg g^{-1} de capacidad de absorción para MNLC y MNLPH, respectivamente. Este estudio mostró un método simple, eficiente y confiable para la eliminación de MB de soluciones acuosas con MNLC y MNLPH como adsorbentes eficientes.

Palabras clave: Azul de Metileno; Café; Cáscara de maní; nanopartículas magnéticas.

Introduction

Enormous amounts of different dyes and pigments are produced for regularly consumption in textile, paper, leather, plastics, food, cosmetics and other industries. Dyes are stable in water and usually resistant to exposure to light and many chemicals. Thus, it is important to find simple and inexpensive procedures for dye removal [1]. MB as a dark green powder is a heterocyclic aromatic chemical that is used widely in biology and chemistry which can cause injuries to humans and animals with symptoms including eyeburns (direct contact), rapid or difficult breathing (inhalation), and also nausea, vomiting, mental confusion and others if ingested [2, 3].

Different chemical and physical treatment methods such as coagulation-flocculation, precipitation, advanced oxidation, ion exchange, membrane filtration, etc have been reported for decolorization of wastewaters. The problem with these methods is the high cost and inadequate performance. Recently, agricultural products and by-products as cheap adsorbents has been widely investigated to introduce instead of current costly methods for removing different types of pollutants (heavy metals ions, hydrocarbons and dyes) from water and wastewaters. Different researchs were done on rice husk [4], peanut husk [5, 6] coffee [7] sawdust [1] banana pith [8], orange peel [9] wheat straw [10], powdered waste sludge [11], wheat shells [12], wheat bran [13] and hen feathers [14]. Modification of agricultural by-product could enhance their natural adsorption capacity [3]. Recently, magnetic separation has been applied in many areas to remove, isolate and/or concentrate the desired components from a sample solution. These technologies are economical, reliable, rapid and durable to treat waste waters by eliminating specific types of pollutants from water [15-19]. Magnetic modification of the low cost adsorbents by magnetic fluids can be leading to formation of magnetic adsorbents which can be easily removed from the treated solutions with magnetic separator.

Peanut husks are one of the biggest food industry waste products. Skin will be separated for processing of peanuts, so a lot of peanut husk is available. Recently, It has been found that peanut husks can efficiently remove copper ions from waste water [20]. So, this study focused on coffee and peanut husk modified with magnetite iron oxide nanoparticles as adsorbents for removal of MB. Peanut in Iran is planted in Golestan, Khuzestan and Guilan provinces. In Guilan province, it is planted mainly in Astaneh Ashrafieh city [21]. Coffee has antioxidant and decrease risk of prostate cancer in men, endometrial cancer in women, liver cancer and diabets and it is useful for hearth. Large amount of coffee produce in the world and most of the people use coffee daily because of its benefites. So the residue of coffee in cafe can be used as a natural adsorbents for elimination of pollution.

The aim of this research is to investigate the usability of magnetic nanoparticles loaded coffee (MNLC) and peanut husk (MNLPH) for MB removal from aqueous solutions.

Materials and methods

Reagents and materials

All used reagents were of analytical reagent grade with the highest purity. MB (Fig. 1) as cationic dye was obtained from Merck (Darmstadt, Germany). Ferric chloride hexahydrate ($\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$), ferrous chloride tetrahydrate ($\text{FeCl}_2 \cdot 4\text{H}_2\text{O}$), hydrochloric acid and perchloric acid were prepared from Merck. Stock solutions of MB were prepared by solving a certain amount of dye in distilled water. These solutions were used for optimization of effective parameters and also for planning calibration curve in order to calculate the dye removal efficiency with UV-V spectrophotometer. All stock and working solutions were prepared using double distilled water.

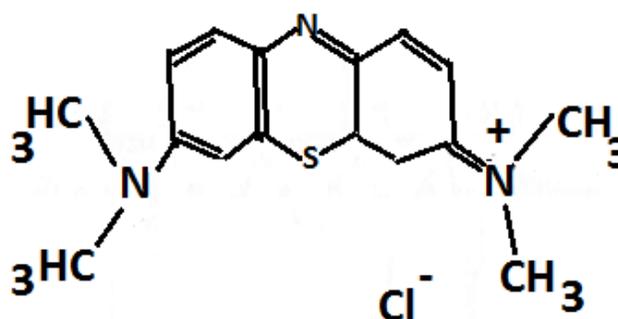


Fig. 1. Chemical structure of methylene blue.

Instrumentation

A Jenway pHmeter (model 370, England) was used for pH measurements. All of the spectrophotometric measurements of MB in the solutions were done at λ_{\max} of MB (660 nm) with a single beam UV-Vis spectrophotometer (Jenway model 6105, England). SEM images, were obtained using digital scanning electron microscope (SEM) (model EM3200, USA). X-ray diffractometer (XRD) (model Xpert MPD, philips, Holland) equipped with a Cu K α radiation source with 2θ range of 0.5-70°, was used for determining of crystal phases and crystallinity of synthesized materials. The infrared spectra of pretreated peanut husk, Coffee and MNLPH, MNLC were recorded in the wave number range of 400-4000 cm^{-1} by Bruker Fourier transform infrared spectrophotometer (FT-IR model Alfa, Germany). Coffee Grinder (model MCG 1575) was used for grinding of Peanut husk and Coffee and rotator (model IKA Ms 3 basic, Germany) was used for mixing. For magnetic separation, a strong super magnet (1×3×5 cm) with 1.4 T magnetic field was applied.

Preparation of the adsorbents

Peanut husk was collected from Astaneh Ashrafieh city. Its salt was removed by washing with water (three times) and then peanut husk was dried in oven at 100°C for 1 h. The husk was milled in a coffee mill and fraction smaller than 0.5 mm in diameter was collected and used for magnetic modification and coffee were obtained locally.

Preparation of magnetite nanoparticles loaded peanut husk and Coffee

Magnetite loaded peanut husk and coffee were prepared in a similar way as magnetic sawdust. Three grams of powdered husk and five grams of coffee were separately added in a 50 mL polypropylene centrifuge tube containing 40 mL of methanol. Then 6 and 5 mL of ferrofluid were added for peanut husk and coffee, respectively. Water-based ionic magnetic fluid stabilized with perchloric acid was prepared using a standard procedure [22]. The suspension was mixed on a rotary mixer (Dynal, Norway) for 1 h. The magnetically modified peanut husk and coffee particles were washed twice with methanol and then air dried [6, 7].

Fig. 2 shows all of the MNLPH and MNLCF adsorbed to magnet and it shows that magnetic nanoparticles loaded natural adsorbents and give them magnetic properties

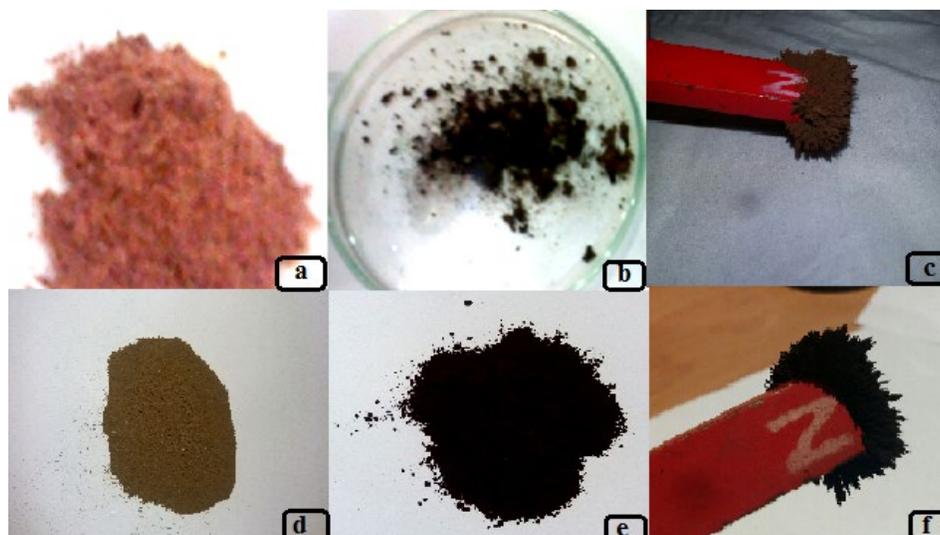
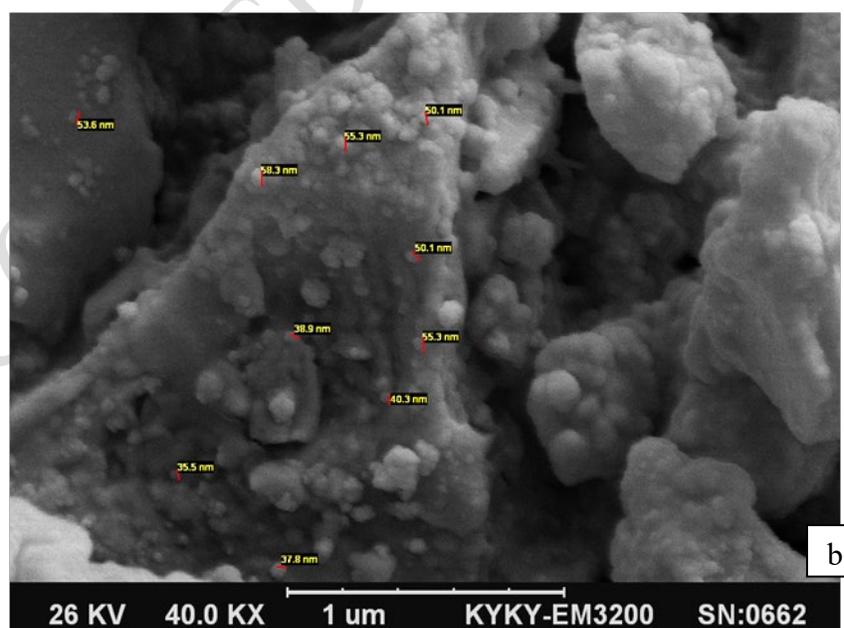


Fig. 2. (a) Peanut husk, (b) MNLPH, (c) MNLPH with magnetically properties. (d) Coffee, (e) MNLCF, (f) MNLCF with magnetically properties.

Result and discussion

Characterization of the MNLC and MNLPH

Characterization of MNLC and MNLPH were studied using XRD and SEM. Fig. 3 shows the SEM images of (a) Coffee, (b) MNLC, (c) pretreated peanut husk and (d) MNLPH. Images indicated that surface of coffee and peanut husk were modified with magnetite nanoparticles in nanometer range and gave it magnetic properties.



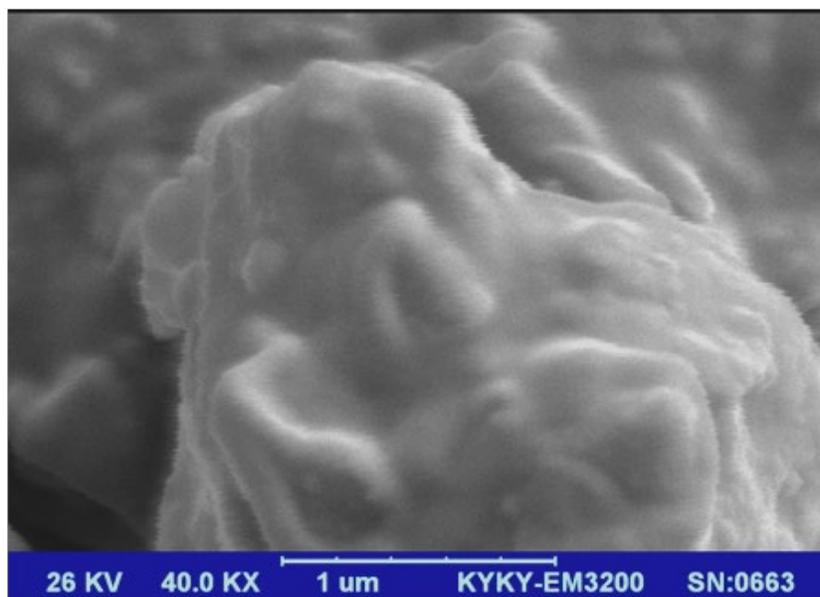


Fig. 3. The SEM image of (a) Coffee, (b) MNLC, (c) pretreated peanut husk and (d) MNLPH.

The XRD pattern of (a) coffee, (b) MNLC and (c) pretreated peanut husk and (d) MNLPH are shown in Fig. 4. XRD patterns for MNLC and MNLPH include all the coffee, peanut husk and magnetite nanoparticles peaks. The results confirm that Fe_3O_4 nanoparticles are successfully impregnated onto coffee and peanut husk. The typical peaks of magnetite are observed that can be assigned to magnetite [15]. The results confirm that coffee and peanut husk surfaces were loaded with iron oxide nanoparticles.

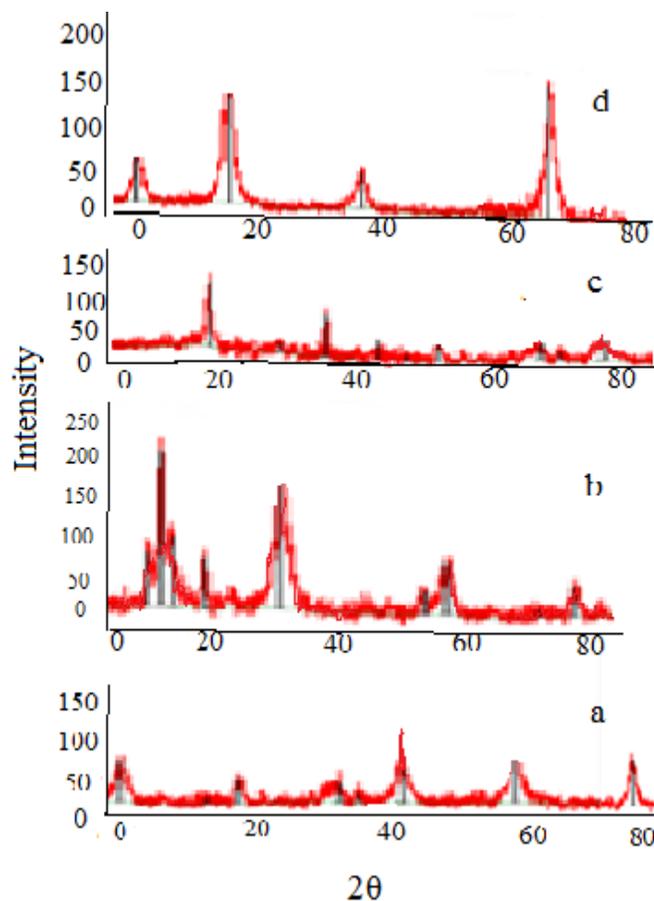


Fig. 4. XRD pattern of (a) coffee, (b) MNLC and (c) pretreated peanut husk and (d) MNLPH.

The FT-IR spectra of (a) coffee and (b) MNLC (c) pretreated peanut husk (d) MNLPH are shown in Fig. 5. The spectra display a number of absorption peaks, indicating the complex nature of coffee and peanut husk. The stretching OH groups, are observed in the wave number range of $3200\text{--}3550\text{ cm}^{-1}$ with strong broad band. The band observed at about $2920\text{--}2850\text{ cm}^{-1}$ could be assigned to the aliphatic C-H groups. The trough at 1600 cm^{-1} represents the benzene ring with C=O. The weaker peak observed at 1378 cm^{-1} corresponds to the aliphatic nitro compound. According to the Fig. 4 (a to d), the same functional groups were detected on the surface of MNLC and MNLPH. Also, the peak for the Fe-O group was observed at 588 cm^{-1} .

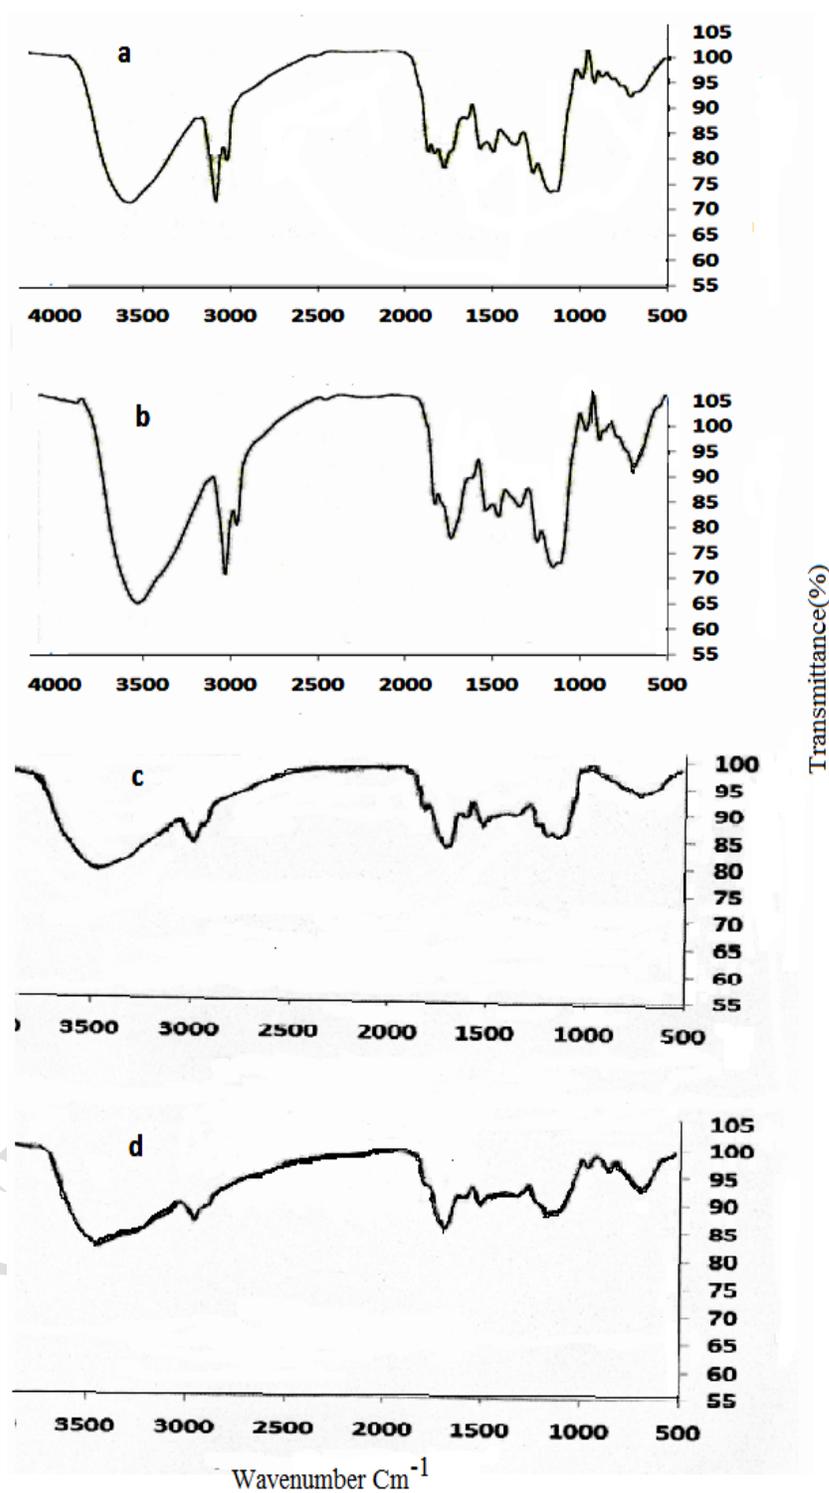


Fig. 5. FT-IR spectra of (a) coffee and (b) MNL(c) pretreated peanut husk (d) MNLPH.

Optimization of dye removal process

In primary experiments the optical absorption behavior of MB at various pHs was studied with measuring absorbance of MB solutions (4 mg L^{-1}) at 660 nm. Various parameters affecting the removal efficiency of MB were studied and optimized to achieve maximum adsorption efficiency. For optimization studies, 0.03 g of adsorbent (MNL or MNLPH) was added to 20 mL solution of MB ($C_{\text{MB}} = 4 \text{ mg L}^{-1}$) in a 50 mL beaker. pH of the solution was adjusted to the desired value using 0.1 mol L^{-1} HCl and NaOH and the solution was stirred for 30 min. After MB adsorption, adsorbent was quickly separated from the sample solutions using a super magnet (1.4 T). The residual MB concentrations in the supernatant clear solution was determined spectrophotometrically using the proper calibration curve. The following equation was applied to calculate the MB removal efficiency in the treatment experiments:

Dye removal efficiency

$$\%R = \frac{c_0 - c_t}{c_0} \times 100 \quad (1)$$

Where, C_0 and C_t are the initial and residual concentrations of the MB.

Effect of amount of adsorbent on the MB removal efficiency

The relationship between adsorption of MB and amount of adsorbent was studied at room temperature and at optimum pH by varying the adsorbent amount from 0.01–0.05 g in contact with 20 mL solution of MB, $C_{\text{MB}} = 4$ and 200 mg L^{-1} for coffee and peanut husk, respectively. The percentage removal increased by increasing the amount of adsorbents due to the increase in contact surface of adsorbent with MB and the greater availability of the adsorbents with increase the number of adsorption sites available for adsorption. Maximum removal of MB reduced with additional increase in adsorbent dose at constant dye concentration and volume. Particles aggregation saturated adsorption sites and decrease sorption capacity. Aggregation would lead to a decrease in total surface area of the adsorbent and increase in diffusional path length. The adsorption reached a maximum value with 0.03 g (1.5 g L^{-1}) of adsorbents. Therefore, 1.5 g L^{-1} of adsorbent was selected as the optimum amount for future experiments (Fig. 6).

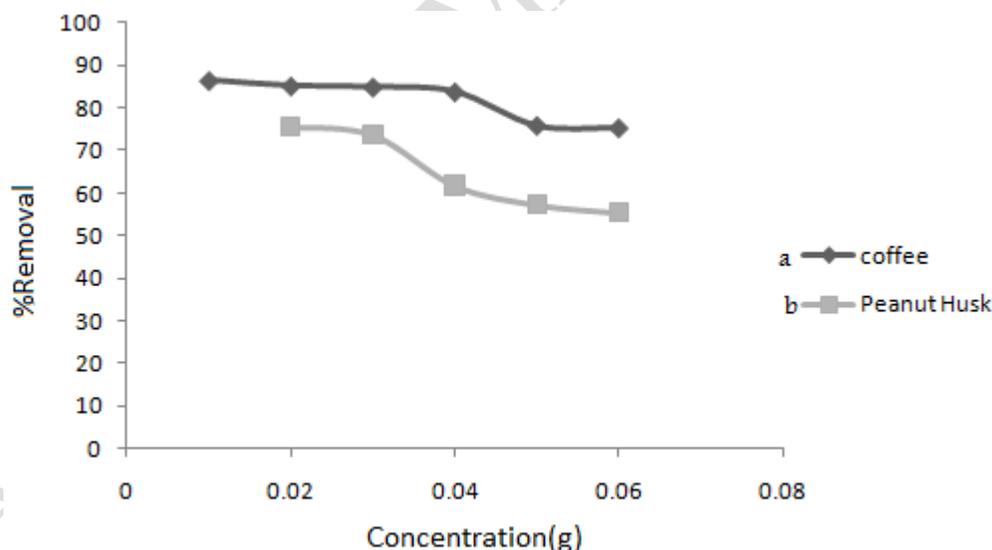


Fig. 6. Effect of concentration of MNL and MNLPH on the MB removal ($C_{\text{MB}} = 4 \text{ mg L}^{-1}$ coffee, $C_{\text{MB}} = 200 \text{ mg L}^{-1}$ peanut husk, $V = 20 \text{ mL}$). (a) coffee and (b) peanut husk.

Effect of contact time on the MB removal efficiency

The effect of contact time on the adsorption of dyes was studied to determine the time taken by adsorbent to remove MB solution $C_{\text{MB}} = 4 \text{ mg L}^{-1}$ for coffee, $C_{\text{MB}} = 200 \text{ mg L}^{-1}$ for peanut husk. Absorbance of

the residual solution at λ_{\max} was measured at different times. It was observed that almost maximum adsorption was occurred after 30 min and this time is enough to reach optimum removal (Fig. 7 (a,b)). Therefore, contact time of 30 min was selected for further works.

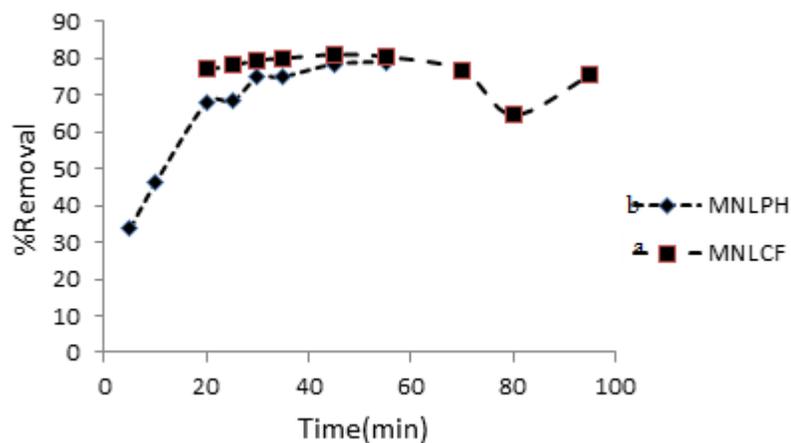


Fig. 7. Effect of contact time on the MB removal ($C_{MB} = 4 \text{ mg L}^{-1}$ coffee, $C_{MB} = 200 \text{ mg L}^{-1}$ peanut husk, $V = 20 \text{ mL}$). (a) coffee and (b) peanut husk

Effect of pH on the MB removal efficiency

Solution pH influences adsorption process by affecting both aqueous chemistry and surface binding-sites of the adsorbent. At low pH values, surface of the adsorbent becomes positively charged because of protonation of the functional groups on adsorbent surface. So adsorption of cationic dye decrease because of electrostatic repulsion between dye and protonated adsorbent. As the pH of the dye solution increases, deprotonation of positively charged groups on the adsorbent occur. Electrostatic attraction between negatively charged sites on the adsorbent and dye cations cause increase in adsorption. The effect of pH on the MB removal efficiency was investigated in the pH range of 3.0–12.0 with a stirring time of 30 min. (Fig. 8 (a,b)) shows the removal efficiency of MB as a function of pH. The adsorption efficiency increased by increasing pH and reached maximum at $\text{pH} = 5.0\text{--}7.5$ for MNLC and $\text{pH} = 5.0\text{--}10.0$ for MNLPH.

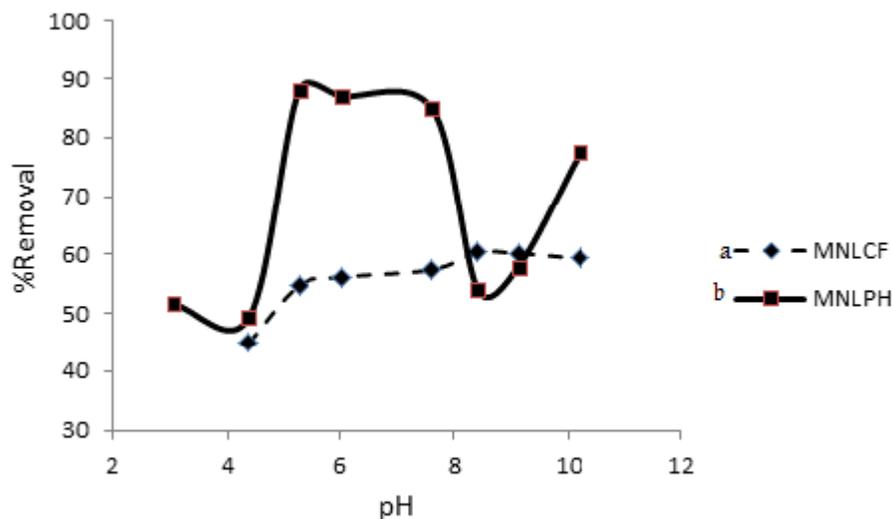


Fig. 8. Effect of PH of solution on the MB removal ($C_{MB} = 4 \text{ mg L}^{-1}$ coffee, $C_{MB} = 200 \text{ mg L}^{-1}$ peanut husk, $V = 20 \text{ mL}$). (a) coffee and (b) peanut husk

Effect of ionic strength and speed of mixing on the MB removal efficiency

The effect of ionic strength on the MB adsorption was investigated by addition of NaCl in the range of 0–10% (w/v). The results (Fig. 9) showed that with increase in the NaCl concentration, the Mb removal was reduced for MNLC, whereas it was increased upto 8-10% (w/v) for MNLPH. Therefore, further experiments were done without salt addition.

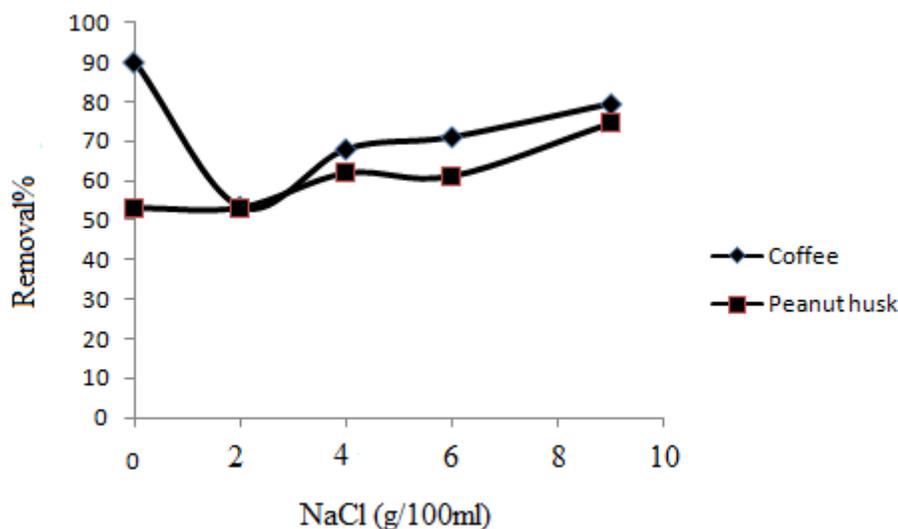


Fig. 9. Effect of ionic strength on the methylene blue removal. ($C_{MB} = 4 \text{ mg L}^{-1}$ coffee, $C_{MB} = 200 \text{ mg L}^{-1}$ peanut husk, $V = 20 \text{ mL}$).

Effect of mixing speed of MB solution and adsorbents on the removal efficiency was studied in the range of 500 to 2500 rpm. The results (Fig. 10) showed that the percent of dye removal was maximum at 1500 rpm due to enhancement in collision between adsorbents and MB dye that increases the adsorption amounts [24]. The rate and speed of MB adsorption on adsorbent depends on thickness of liquid film surrounding adsorbent that is affected by speed of mixing. Percent of removal of MB increased with increase in mixing speed in the range of 500 to 1500 rpm and was maximum at 1500 rpm, but at rates higher than 1500 rpm the removal percent was reduced. It is related to insignificant effect of film thickness in the mixing speed higher than 1500 rpm, hence agitation rate of 1500 rpm was selected for all of the future experiments.

Adsorption mechanism

The most important issue in adsorption research is understanding mechanism of adsorption. Structure of the adsorbate and adsorbent surface properties should be considered. MB is a cationic dye and in aqueous solution it separates as two ions MB^+ and Cl^- . A chemical interaction between hydroxyl groups of Fe_3O_4 magnetic nanoparticles and dye ions occurs.

Based on the research findings, and due to the structure of the adsorbate and adsorbent surface properties, the adsorption mechanism of MB onto MNLPH and MNLCF may be done according to the following steps:

- Movement of MB dye from the solution to the surface of the adsorbent
- Diffusion of MB dye through the boundary layer to the surface of the adsorbent
- Adsorption of MB dye on the surface of MNLPH and MNLCF, which may be due to the formation of surface hydrogen bonds between the hydroxyl groups of the magnetic nanoparticles and the nitrogen atoms of MB.

Possible mechanism can be shown as below:

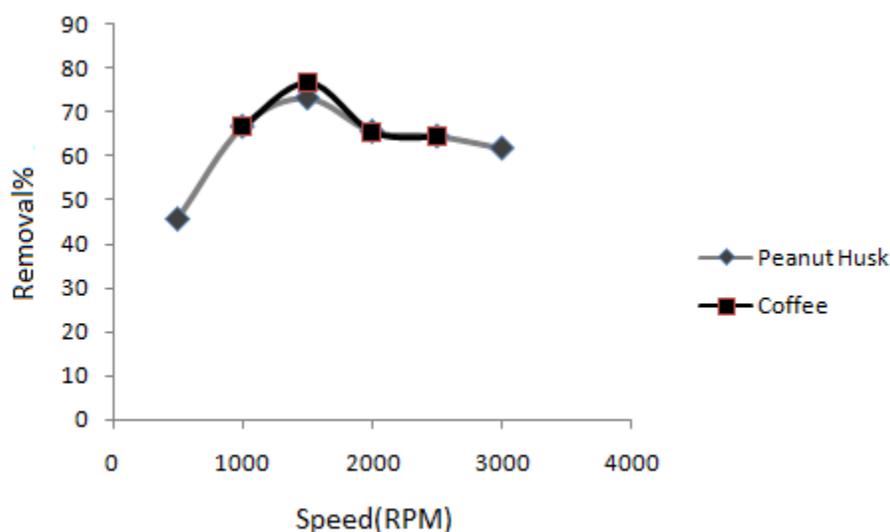


Fig. 10. Effect of mixing speed on the removal efficiency of MB ($C_{\text{MB}} = 4 \text{ mg L}^{-1}$ coffee, $C_{\text{MB}} = 200 \text{ mg L}^{-1}$ peanut husk, $V = 20 \text{ mL}$).

Kinetic and isotherm of adsorption

The study of kinetics of MB adsorption onto MNLC and MNLPH adsorbents is required for selecting optimum operating conditions for the full-scale bath processes. The kinetic parameters, which are helpful for the prediction of the adsorption rate, give important information for designing and modeling the adsorption processes. The kinetic data for adsorption onto MNLC and MNLPH were analyzed using pseudo-first, pseudo-second order, Elovich and intra-particle diffusion models to find out the adsorption rate expression. In the present study, kinetic studies were performed at concentrations of 20 - 100 mg L^{-1} of MB for MNLC and MNLPH and the solutions were stirred in the time intervals ranged from 0 to 70 min. Then, the clear supernatant solutions were spectrophotometrically measured for residual MB concentration in the solution. Fig. 11 shows the equilibrium concentrations of MB at the adsorption time interval of 0–70 min. The concentration of residual MB in the solution was monitored and the adsorption capacity q_t at time t ($q_t, \text{mg g}^{-1}$) was calculated by the following equation:

$$q_t = \frac{(C_0 - C_t) \times V}{w} \quad (2)$$

Where C_0 and C_t are the initial and equilibrium concentrations of MB at a given time t (mg L^{-1}), respectively. Also, v is the solution volume (mL) and w is the weight of the adsorbent (g).

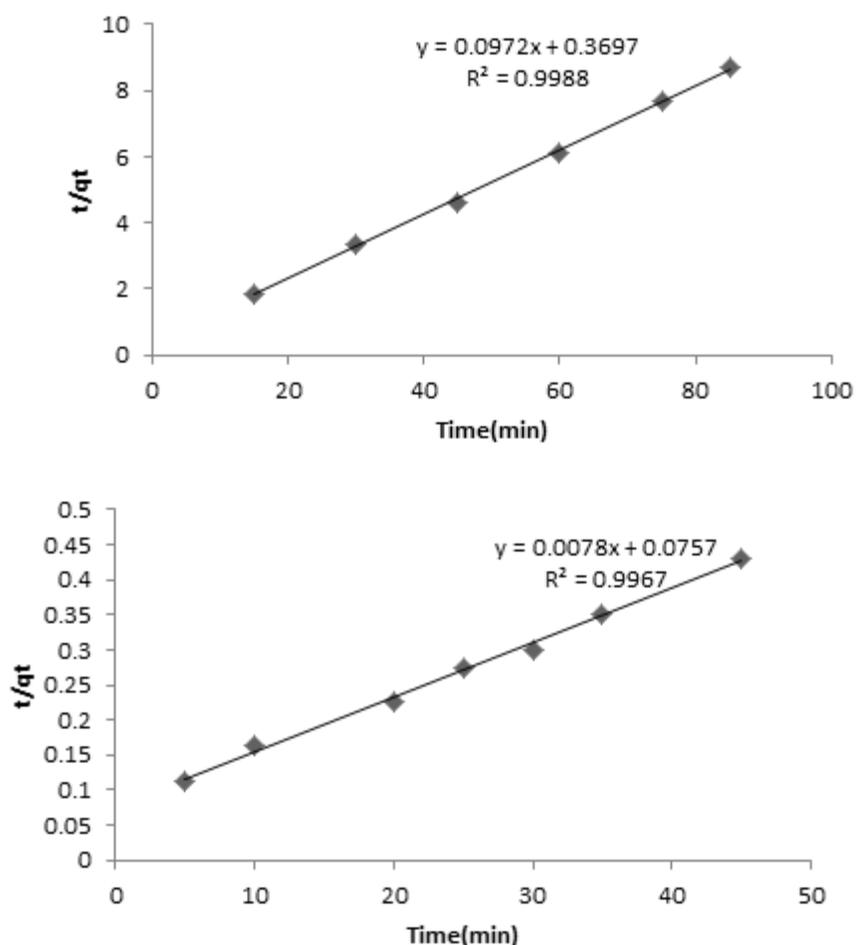


Fig. 11. Fitting of kinetic data to the pseudo-second order kinetic model ($C_{MB}=4 \text{ mg L}^{-1}$ for coffee (a) and 200 mg L^{-1} for peanut husk (b) MNL, MNLPH= 0.03 g, pH=7).

According to the results, the removal rate was very fast during the initial stages of the adsorption process. The kinetic of adsorption was obeyed from pseudo-second order kinetic model according to following equation. The rate of pseudo-second order reaction may be dependent on the amount of solute adsorbed on the surface of adsorbent and the adsorbed amount at equilibrium. The kinetic rate equations for pseudo-second order kinetic model can be written as follows:

$$\frac{t}{q_t} = \frac{1}{k_2 q_e^2} + \left[\frac{1}{q_e}\right]t \quad (3)$$

where q_t and q_e , are the value of adsorbed MB at each time and at equilibrium and k_2 ($\text{g mg}^{-1} \text{ min}^{-1}$) is the pseudo-second order rate constant. If the second order kinetic equation is applicable, the plot of t/q_t against t (Eq(3)) should give a linear relationship. The q_e and k_2 can be determined from the slope and intercept of the plot. Fitting of kinetic data to pseudo-second order kinetic model, was shown in Fig. 11(a,b). The best fit of the pseudo-second order kinetic model (R^2 close to 1) in the present system shows the adsorption of MB followed by chemisorptions mechanism via electrostatic attraction.

Equilibrium isotherm equations are used to describe the experimental sorption data. The parameters obtained from the different models provide important information on the sorption mechanisms and the surface properties and affinities of the sorbent. The equilibrium adsorption isotherm was determined using batch studies. 20 mL of the MB solution with various initial dye concentrations in the range of $50\text{--}500 \text{ mg L}^{-1}$, was

poured into a glass bottle. The time required to reach equilibrium as determined in equilibrium studies was 30 min. The amount of dye uptake by the MNLC and MNLPH, q_e (mg g^{-1}), was obtained by Eq. (2). Adsorption data obtained in a concentration range of 50–500 mg L^{-1} were correlated with the following linear forms of Langmuir (Eq. (4))[25],

Freundlich (Eq. (5))[26] and Temkin (Eq. (6))[27] adsorption isotherm models:

$$\text{Langmuir equation: } \frac{c_e}{q_e} = \frac{1}{K_L q_{\max}} + \frac{1}{q_{\max}} c_e \quad [4]$$

$$\text{Freundlich equation: } \log q_e = \log K_f + \frac{1}{n} \log c_e \quad [5]$$

$$\text{Temkin equation: } q_e = K_1 \cdot \ln(K_2) + K_1 \cdot \ln(c_e) \quad [6]$$

where q_e is the equilibrium concentration of MB on the adsorbent (mg g^{-1}), C_e is the equilibrium concentration of MB in the solution (mg L^{-1}), q_{\max} is the monolayer capacity of the adsorbent (mg g^{-1}), K_L the Langmuir constant (L mg^{-1}) and related to the free energy of adsorption, K_F is the Freundlich constant (L g^{-1}) and n (dimensionless) is the heterogeneity factor.

K_1 is related to the heat of adsorption (L g^{-1}) and K_2 is the dimensionless Temkin isotherm. In the Langmuir model, a plot of C_e/q_e versus C_e should indicate a straight line of slope $1/q_{\max}$ and an intercept of $1/(K_L q_{\max})$. The correlation coefficient ($R^2_{\text{Langmuir}} = 0.949$, $R^2_{\text{Freundlich}} = 0.8993$) for Coffee and ($R^2_{\text{Langmuir}} = 0.9898$, $R^2_{\text{Freundlich}} = 0.4682$) for peanut husk showed strong positive evidence on the adsorption of MB onto adsorbents follows the Langmuir isotherm. This indicates that the adsorption of MB occurs on a homogenous surface by monolayer adsorption without any interaction between adsorbed ions. The value of Q_{\max} for adsorption of MB was obtained from the Langmuir model as 88.49 and 74.62 mg g^{-1} for MNLC and MNLPH, respectively.

Conclusion

The sorption of pollutants from aqueous solutions plays a significant role in water pollution control. For this purpose, the utilization of the MNLC and MNLPH as efficient adsorbents was successfully carried out to remove the MB from aqueous samples. The adsorption followed the pseudo-second order kinetic model, suggesting chemisorption. The fit of the Langmuir model in the present system shows the formation of a monolayer covering of the adsorbate at the outer space of the adsorbent. The MNLC and MNLPH are synthesized easily. Due to their very high surface areas, high adsorption capacity can be achieved. The data reported here should be useful for the design and fabrication of an economically treatment process for dye adsorption in industrial effluents.

Acknowledgments

This research is the result of research project No. 7/36027 dated 1/7/2015 of the Vice-Chancellor of Research of the University of Guilan. The authors extend their sincere thanks to University of Guilan for its funding of this research.

References

1. Safarik, I., Lunackova, P., Mosiniewicz-Szablewska, E., Weyda, F., and Safarikova, M. (2007). Adsorption of water-soluble organic dyes on ferrofluid modified sawdust. *Holzforchung*. 61, 247.
2. Kaewprasit, C., Hequet, E., Abidi, N., and Gourlot, J.P. (1998). Application of methylene blue adsorption to cotton fiber specific surface area measurement. *Cot Sci*. 2, 164.
3. Ghosh, D., Bhattacharyya, K.G. (2002) Adsorption of methylene blue on kaolinite *Appl. clay Sci*. 20, 295.
4. Chakraborty, S., Chowdhury, S., and Saha, P. Das. (2011). Adsorption of Crystal Violet from aqueous solution onto NaOH-modified rice husk. *J. Carbohydr. Polym*. 86, 1533.

5. Liu, Y., Sun, X., and Li, B. (2010). Adsorption of Hg^{2+} and Cd^{2+} by ethylenediamine modified peanut shell. *J. Carbohydr. Polym.* 81, 335.
6. Safarik, I., and Safarikova, M. (2010). Magnetic fluid modified peanut husks as an adsorbent for organic dyes removal. *Phys. Proced.* 9, 274.
7. Safarik, I., Horska, K., Svobodova, B., and Safarikova, M. (2012). Magnetically modified spent coffee grounds for dyes removal. *Eur. Food. Res. Technol.* 234, 345.
8. Namasivayam, C., and Kanchana, N. (1992). Waste banana pith as adsorbent for color removal from wastewaters. *Chemosphere.* 25, 1691.
9. Namasivayam, C., Muniasamy, N., Gayatri, K., Rani, M., and Ranganathan, K. (1996). Removal of dyes from aqueous solutions by cellulosic waste orange peel. *Bioresour. Technol.* 57, 37.
10. Robinson, T., Chandran, B., and Nigam, P. (2002). Removal of dyes from a synthetic textile dye effluent by biosorption on apple pomace and wheat straw. *Water Res.* 36, 2824.
11. Serpil, O., and Fikret, K. (2006). Utilization of powdered waste sludge (PWS) for removal of textile dyestuffs from wastewater by adsorption. *Environ. Manage.* 81, 307.
12. Bulut, Y., Gozubenli, N.N., and Aydin, H. (2007). Equilibrium and kinetics studies for adsorption of direct blue 71 from aqueous solution by wheat shells. *J. Hazard. Mater.* 144, 300.
13. Sulak, M.T., Demirbas, E., and Kobya, M. (2006). Removal of astrazon yellow 7GL from aqueous solutions by adsorption onto wheat bran. *Bioresour. Technol.* 98, 2590.
14. Mittal, A., Kurup, L., and Mittal, J. (2007). Freundlich and Langmuir adsorption isotherms and kinetics for the removal of tartrazine from aqueous solutions using hen feathers. *J. Hazard. Mater.* 146, 243.
15. Oliveira, L.C.A., Rios, R.V., Fabris, J.D., Sapag, K., Garg, V.K., and Lago, R.M. (2003). Clay-iron oxide magnetic composites for the adsorption of contaminants in water. *Appl. Clay. Sci.* 22, 169.
16. Bandari, F., Safa, F., and Shariati, Sh. (2015). Application of response surface method for optimization of adsorptive removal of eriochrome black T using magnetic multi-wall carbon nanotube nanocomposite. *Arab. J. Sci. Eng.* 40, 3363.
17. Golshekan, M., and Shariati, Sh. (2013). Nano Magnetic Solid Phase Extraction for Preconcentration of Lead Ions in Environmental Samples by a Newly Synthesized Reagent. *Acta. Chim. Slov.* 60, 358.
18. Manoochehri, M., Mostashari, S.M., and Shariati, S.H. (2013). Lignin removal from aqueous solutions using Fe_3O_4 magnetic nanoparticles as recoverable adsorbent. *Cell. Chem. Tech.* 47, 727.
19. Shariati, Sh., Faraji, M., Yamini, Y., and Rajabi, A. (2011). Fe_3O_4 magnetic nanoparticles modified with sodium dodecyl sulfate for removal of safranin O dye from aqueous solutions. *Desalination.* 270, 160.
20. Ozsoy, H.D., Kumbur, H., and Ozer, Z. (2007). Adsorption of copper(II) ions to peanut hulls and *Pinus brutiasawdust*. *Int J. Environ. Pollut.* 31, 125.
21. Ashoori, D., Noorhosseini, S.A., and Noorhosseini, S.F. (2014). Effective factors on development decline of production and packaging peanut crop in Astaneh-Ashrafieh, *Biosci. J.B.* 41, 96.
22. Massart, R. (1981). Preparation of aqueous magnetic liquids in alkaline and acidic media. *IEEE Trans Magn.* 17, 1247.
23. Alberghina G., Bianchini R., fichera M., Fisichella S., *Dimerization of cibacorn blue F3GA and other dyes influences of salts and temperature.*, 2000, 46, 129.
24. Kusmierek, K. And Swiatkowski, A. (2015) The influence of different agitation techniquea on the adsorption kinetics of 4 chlrophenol on granular activated carbon. *Reac kinet mech cat.* 116, 261.
25. Langmuir, I. (1918). The adsorption of gases on plane surfaces of glass, mica and platinum, *Am. Chem. Soc.* 40, 1361.
26. Freundlich, H.M.F. (1906). Over the adsorption in solution. *Z. Phys. Chem.* 57, 385.
27. Tempkin, M.J., and Pyzhev, V. (1940). Recent modifications to langmuir isotherms. *Acta Physiol. Chem. USSR.* 12, 271.
28. Oliveira, L.S., Franca, A.S., Alves, T.M. and Rocha, S.D.F. (2008). Evaluation of untreated coffee husks as potential biosorbents for treatment of dye contaminated waters. *J. Hazard. Mater.* 155, 507.
29. Pavan, F.A., Lima, E.C., Dias, S.L.P., and Mazzocato, A.C. (2008). Methylene blue biosorption from aqueous solutions by yellow passion fruit waste. *J. Hazard. Mater.* 150, 703.
30. Vadivelan, V., and Kumar, K.V. (2005). Equilibrium, kinetics, mechanism and process design for the sorption of methyleneblue on to rice husk. *J. Colloid Interf. Sci.* 286, 90.
31. Annadurai, G., Juang, R.S., and Lee, D.J. (2002). Use of cellulose-based wastes for adsorption of dyes from aqueous solutions. *J. Hazard. Mater.* 92, 263.

32. Han,R., Wang,Y., Han,P., Shi,J., Yang,J., and Lu,Y.(2006).Removal of methylene blue from aqueous solution by chaff in batch mode. *J.Hazard. Mater.* 137, 550.
33. Franca,A.S., Oliveira,L.S., and Ferreira, M.E.(2009).Kinetics and equilibrium studies of methylene blue adsorption by spent coffee grounds. *Desalination.*249, 267.
34. Bulut,Y., and Aydin,H. (2006). Study of methylene blue adsorption on wheat shell. *Desalination.* 194, 259.
35. Ncibi,M.C., Mahjoub,B., and Seffen,M.(2007).Kinetic and equilibrium studies of methylene blue biosorption by posidonia oceanica(L.) fibers. *J. Hazard.Mater.* 139, 280.

Symbols

MNLC: magnetite nanoparticles loaded coffee.
MNLPH: magnetite nanoparticles loaded and peanut husk.
MB: methylene blue
 q_e : Equilibrium dye concentration on the adsorbent.
 C_e : Equilibrium dye concentration in the solution.
 q_{max} : monolayer capacity of the adsorbent.
 K_L : Langmuir constant.
 K_F : Freundlich constant.
N: Degree of nonlinearity of adsorption.

ACCEPTED MANUSCRIPT